



IEC 60794-1-23

Edition 2.0 2019-10

INTERNATIONAL STANDARD

NORME INTERNATIONALE



**Optical fibre cables –
Part 1-23: Generic specification – Basic optical cable test procedures – Cable
element test methods**

**Câbles à fibres optiques –
Partie 1-23: Spécification générique – Procédures fondamentales d'essai des
câbles optiques – Méthodes d'essai des éléments de câble**





THIS PUBLICATION IS COPYRIGHT PROTECTED
Copyright © 2019 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

Droits de reproduction réservés. Sauf indication contraire, aucune partie de cette publication ne peut être reproduite ni utilisée sous quelque forme que ce soit et par aucun procédé, électronique ou mécanique, y compris la photocopie et les microfilms, sans l'accord écrit de l'IEC ou du Comité national de l'IEC du pays du demandeur. Si vous avez des questions sur le copyright de l'IEC ou si vous désirez obtenir des droits supplémentaires sur cette publication, utilisez les coordonnées ci-après ou contactez le Comité national de l'IEC de votre pays de résidence.

IEC Central Office
3, rue de Varembe
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
info@iec.ch
www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigendum or an amendment might have been published.

IEC publications search - webstore.iec.ch/advsearchform

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee,...). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and once a month by email.

IEC Customer Service Centre - webstore.iec.ch/csc

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: sales@iec.ch

Electropedia - www.electropedia.org

The world's leading online dictionary on electrotechnology, containing more than 22 000 terminological entries in English and French, with equivalent terms in 16 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

IEC Glossary - std.iec.ch/glossary

67 000 electrotechnical terminology entries in English and French extracted from the Terms and Definitions clause of IEC publications issued since 2002. Some entries have been collected from earlier publications of IEC TC 37, 77, 86 and CISPR.

A propos de l'IEC

La Commission Electrotechnique Internationale (IEC) est la première organisation mondiale qui élabore et publie des Normes internationales pour tout ce qui a trait à l'électricité, à l'électronique et aux technologies apparentées.

A propos des publications IEC

Le contenu technique des publications IEC est constamment revu. Veuillez vous assurer que vous possédez l'édition la plus récente, un corrigendum ou amendement peut avoir été publié.

Recherche de publications IEC -

webstore.iec.ch/advsearchform

La recherche avancée permet de trouver des publications IEC en utilisant différents critères (numéro de référence, texte, comité d'études,...). Elle donne aussi des informations sur les projets et les publications remplacées ou retirées.

IEC Just Published - webstore.iec.ch/justpublished

Restez informé sur les nouvelles publications IEC. Just Published détaille les nouvelles publications parues. Disponible en ligne et une fois par mois par email.

Service Clients - webstore.iec.ch/csc

Si vous désirez nous donner des commentaires sur cette publication ou si vous avez des questions contactez-nous: sales@iec.ch

Electropedia - www.electropedia.org

Le premier dictionnaire d'électrotechnologie en ligne au monde, avec plus de 22 000 articles terminologiques en anglais et en français, ainsi que les termes équivalents dans 16 langues additionnelles. Egalement appelé Vocabulaire Electrotechnique International (IEV) en ligne.

Glossaire IEC - std.iec.ch/glossary

67 000 entrées terminologiques électrotechniques, en anglais et en français, extraites des articles Termes et Définitions des publications IEC parues depuis 2002. Plus certaines entrées antérieures extraites des publications des CE 37, 77, 86 et CISPR de l'IEC.



IEC 60794-1-23

Edition 2.0 2019-10

INTERNATIONAL STANDARD

NORME INTERNATIONALE



**Optical fibre cables –
Part 1-23: Generic specification – Basic optical cable test procedures – Cable
element test methods**

**Câbles à fibres optiques –
Partie 1-23: Spécification générique – Procédures fondamentales d'essai des
câbles optiques – Méthodes d'essai des éléments de câble**

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

COMMISSION
ELECTROTECHNIQUE
INTERNATIONALE

ICS 33.180.10

ISBN 978-2-8322-7407-1

**Warning! Make sure that you obtained this publication from an authorized distributor.
Attention! Veuillez vous assurer que vous avez obtenu cette publication via un distributeur agréé.**

CONTENTS

FOREWORD.....	5
1 Scope.....	7
2 Normative references	7
3 Terms and definitions	7
4 General requirements	8
5 Method G1: Bend test for optical cable elements	8
5.1 Object.....	8
5.2 Sample	8
5.3 Apparatus	8
5.4 Procedure	8
5.5 Requirements	8
5.6 Details to be specified.....	8
6 Method G2: Ribbon dimensions and geometry – Visual method	9
6.1 Object.....	9
6.2 Sample	9
6.3 Apparatus	9
6.4 Procedure	9
6.4.1 General	9
6.4.2 Method 1	9
6.4.3 Method 2	9
6.5 Requirements	9
6.6 Details to be specified.....	9
6.7 Definitions of ribbon dimensions and geometry	10
6.7.1 General	10
6.7.2 Width and height.....	10
6.7.3 Basis line.....	10
6.7.4 Fibre alignment.....	10
7 Method G3: Ribbon dimensions – Aperture gauge	11
7.1 Object.....	11
7.2 Sample	11
7.3 Apparatus	11
7.4 Procedure	11
7.5 Requirement	11
7.6 Details to be specified.....	11
8 Method G4: Ribbon dimensions – Dial gauge (obsoleted method).....	12
9 Method G5: Ribbon tear (separability)	12
9.1 Object.....	12
9.2 Sample	12
9.3 Apparatus	13
9.4 Procedure	13
9.5 Requirements	14
9.6 Details to be specified.....	14
10 Method G6: Ribbon torsion	14
10.1 Object.....	14
10.2 Sample	14

10.3	Apparatus	14
10.4	Procedure	15
10.5	Requirements	15
10.6	Details to be specified	15
11	Method G7: Tube kinking	16
11.1	Object	16
11.2	Sample	16
11.3	Apparatus	16
11.4	Procedure	17
11.5	Requirements	17
11.6	Details to be specified	17
12	Method G8: Ribbon residual twist test	18
12.1	Object	18
12.2	Sample	18
12.3	Apparatus	18
12.4	Procedure	18
12.5	Requirements	18
12.6	Details to be specified	19
13	Method G9: Bleeding and evaporation	19
13.1	Object	19
13.2	Sample	19
13.3	Apparatus	19
13.4	Procedure	20
13.5	Requirements	20
13.6	Details to be specified	21
14	Method G10A: Stripping force stability of cabled optical fibres	21
14.1	Object	21
14.2	Sample	21
14.2.1	Sample length	21
14.2.2	Sample preparation	21
14.3	Apparatus	21
14.4	Procedure	21
14.5	Requirements	21
14.6	Details to be specified	22
15	Method G10B: Strippability of optical fibre ribbons	22
15.1	Object	22
15.2	Sample	22
15.3	Apparatus	22
15.3.1	General	22
15.3.2	Stripping tool	22
15.3.3	Motor and slide (if used)	23
15.4	Positioning and holding equipment	23
15.5	Alcohol wipe	23
15.6	Procedure	23
15.7	Requirements	24
15.8	Details to be specified	24
16	Method G10C: Strippability of buffered optical fibres	24
16.1	Object	24

16.2	Sample	24
16.3	Apparatus	24
16.4	Procedure	24
16.5	Requirements	25
16.6	Details to be specified	25
17	Method G11A: Tensile strength and elongation of buffer tubes and micro tubes at break	25
17.1	Object	25
17.2	Sample	25
17.2.1	General	25
17.2.2	Preparation and conditioning of test pieces	25
17.2.3	Determination of cross-sectional area	28
17.2.4	Ageing treatment	29
17.3	Apparatus	29
17.4	Procedure	30
17.5	Requirements	31
18	Method G11B: Elongation of buffer tubes and micro tubes at low temperature	31
18.1	Object	31
18.2	Sample	31
18.2.1	General	31
18.2.2	Preparation of test pieces	31
18.3	Apparatus	32
18.4	Procedure	32
18.5	Requirements	33
18.6	Details to be specified	33
	Bibliography	34
	Figure 1 – Cross-sectional drawing illustrating fibre ribbon geometry	10
	Figure 2 – Aperture gauge	11
	Figure 3 – Sample preparation for ribbon separability test	13
	Figure 4 – Separability procedure	14
	Figure 5 – Torsion test	15
	Figure 6 – Tube kinking test	16
	Figure 7 – Bleeding and evaporation test set-up	20
	Figure 8 – Dumb-bell test piece	27
	Figure 9 – Small dumb-bell test piece	28
	Figure 10 – Punch end showing groove	28
	Figure 11 – Test pieces cut by grooved punch	28
	Figure 12 – Machine for preparing test pieces	30
	Table 1 – Examples of test apparatus dimensions for tube kinking	17
	Table 2 – Condition of stripped samples	23

INTERNATIONAL ELECTROTECHNICAL COMMISSION

OPTICAL FIBRE CABLES

Part 1-23: Generic specification – Basic optical cable test procedures – Cable element test methods

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

International Standard IEC 60794-1-23 has been prepared by subcommittee 86A: Fibres and cables, of IEC technical committee 86: Fibre optics.

This second edition cancels and replaces the first edition published in 2012. It constitutes a technical revision.

This edition includes the following significant technical changes with respect to the previous edition:

- a) addition of a new test method G9: Bleeding and evaporation (formerly known as method E15 in IEC 60794-1-21:2015);
- b) addition of a new test method G10A: Stripping force stability of cabled optical fibres (formerly known as method E5A in IEC 60794-1-21:2015);
- c) addition of a new test method G10B: Strippability of optical fibre ribbons (formerly known as method E5B in IEC 60794-1-21:2015);
- d) addition of a new test method G10C: Strippability of buffered optical fibres (formerly known as method E5C in IEC 60794-1-21:2015);

- e) addition of a new test method G11A: Tensile strength and elongation of buffer tubes (included in IEC 60811-501);
- f) addition of a new test method G11B: Elongation of buffer tubes at low temperature (included in IEC 60811-505);
- g) clarification of the sample preparation procedure in method G5: Ribbon tear (separability);

The text of this International Standard is based on the following documents:

CDV	Report on voting
86A/1912/CDV	86A/1945/RVC

Full information on the voting for the approval of this International Standard can be found in the report on voting indicated in the above table.

This document has been drafted in accordance with the ISO/IEC Directives, Part 2.

A list of all parts in the IEC 60794 series, published under the general title *Optical fibre cables*, can be found on the IEC website.

The committee has decided that the contents of this document will remain unchanged until the stability date indicated on the IEC website under "<http://webstore.iec.ch>" in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

IMPORTANT – The 'colour inside' logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

OPTICAL FIBRE CABLES

Part 1-23: Generic specification – Basic optical cable test procedures – Cable element test methods

1 Scope

This part of IEC 60794 describes test procedures to be used in establishing uniform requirements for the geometrical, material, mechanical, environmental properties of optical fibre cable elements.

This document applies to optical fibre cables for use with telecommunication equipment and devices employing similar techniques, and to cables having a combination of both optical fibres and electrical conductors.

Throughout the document, the wording "optical cable" can also include optical fibre units, microduct fibre units, etc.

NOTE The environmental testing of optical fibre ribbon would be valuable for some applications. Useful information about suitable test methods can be found in the optical fibre standards IEC 60793-1-50, IEC 60793-1-51, IEC 60793-1-52, and IEC 60793-1-53.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60794-1-2, *Optical fibre cables – Part 1-2: Generic specification – Basic optical cable test procedures – General guidance*

IEC 60794-1-31:2018, *Optical fibre cables – Part 1-31: Generic specification – Optical cable elements – Optical fibre ribbon*

IEC 60793-1-32:2018, *Optical fibres – Part 1-32: Measurement methods and test procedures – Coating strippability*

IEC 60793-1-40, *Optical fibres – Part 1-40: Attenuation measurement methods*

IEC 60793-1-46, *Optical fibres – Part 1-46: Measurement methods and test procedures – Monitoring of changes in optical transmittance*

IEC 60811-401, *Electric and optical fibre cables – Test methods for non-metallic materials – Part 401: Miscellaneous tests – Thermal ageing methods – Ageing in an air oven*

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

4 General requirements

IEC 60794-1-2 is the reference guide to test methods of all types. It shall be considered for general requirements and definitions.

5 Method G1: Bend test for optical cable elements

5.1 Object

The purpose of this test is to characterize cable elements for splicing purposes by determining the attenuation increase of an optical cable element (fibre, ribbon, core tube, breakout unit, etc.) when bent within a splice closure or similar device.

5.2 Sample

The length of the sample of optical cable element shall be sufficient to carry out the testing specified.

5.3 Apparatus

The apparatus consists of

- a) a mandrel having a smooth surface with diameter as stated in the detail specification, and
- b) an attenuation measuring apparatus for the determination of attenuation change (according to the test methods of IEC 60793-1-40 and IEC 60793-1-46).

5.4 Procedure

The element to be tested shall be wound on the mandrel at minimal tension; the number of turns shall be stated in the detail specification.

In order to measure the attenuation increase caused by bending, allowance should be made for the intrinsic attenuation of the fibre.

5.5 Requirements

Any increase in attenuation shall comply with the limits shown in the detail specification.

5.6 Details to be specified

The detail specification shall include the following:

- optical test wavelength;
- diameter of the mandrel;
- number of turns;
- apparatus and attenuation measuring technique;
- temperature at which the evaluation shall be performed if different from room temperature.

6 Method G2: Ribbon dimensions and geometry – Visual method

6.1 Object

The purpose of this test is to determine the geometry of an optical fibre ribbon as defined by the parameters of width, height and fibre alignment, for the purpose of type testing to assume proper manufacturing process control. This test is not necessarily suitable for final product inspection and, unless otherwise specified, shall not be used for that purpose.

6.2 Sample

The number of samples to be tested shall be specified in the detail specification. The selected samples shall be statistically independent and representative of the ribbon population tested.

6.3 Apparatus

The apparatus consists of a microscope or profile projector with appropriate magnification.

6.4 Procedure

6.4.1 General

Either of the two procedure methods described in 6.4.2 and 6.4.3 may be used.

For the specified number of samples, all dimensions shall be measured as average as well as maximum and minimum values.

Care should be taken that the preparation of the sample does not change the structure of the fibre ribbon and represents an undisturbed image of the fibre cladding and ribbon cross-section.

6.4.2 Method 1

The sample is prepared by cutting it perpendicular to the axis of the ribbon and placing it in a curable resin or in a tool which holds the ribbon. If necessary, the sample shall be ground and polished to prepare a smooth perpendicular end face. The prepared sample is secured with its end face perpendicular to the optical path and measured by means of a microscope or profile projector.

6.4.3 Method 2

Place the ribbon in a ribbon fibre holder and remove 20 mm to 25 mm of the fibre coating and matrix material with the ribbon hot sheath stripping tool and wipe the stripped portion of the fibres clean with an alcohol-moistened pad. Adjust the position of the ribbon in the ribbon fibre holder and cleave the fibres at a distance of 250 μm to 500 μm from the stripped edge of the ribbon. Cut and polish the other end of the ribbon, and illuminate it with a collimated light source. Align and measure the cleaved end of the ribbon under microscope.

6.5 Requirements

Unless otherwise specified in the detail specification, the width, height and fibre alignment shall be in accordance with IEC 60794-1-31:2018.

6.6 Details to be specified

The detail specification shall include the following:

- a) permissible maximum and minimum values;
- b) limits for average values;
- c) number of samples tested.

6.7 Definitions of ribbon dimensions and geometry

6.7.1 General

The following definitions apply to a fibre ribbon cross-section as shown in Figure 1. The figure illustrates an example for a 4-fibre ribbon, where a is the diameter of a coloured fibre.

NOTE In consideration of the precision of fibre geometric attributes and the relatively larger precision of ribbon geometry requirements, it is acceptable for glass core/glass cladding fibres to use the edge of the cladding for the measurements of 6.7.3 and 6.7.4 in lieu of the fibre centres. In this case, the measurements can be made on the same side of all fibres (e.g. top or bottom, left or right side).

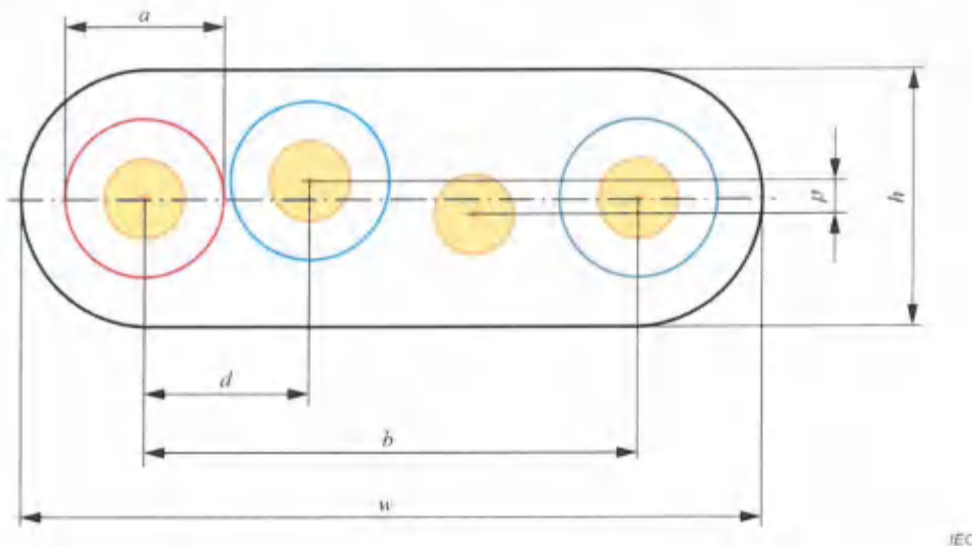


Figure 1 – Cross-sectional drawing illustrating fibre ribbon geometry

6.7.2 Width and height

The width w and height h of the ribbon are the dimensions of the minimum rectangular area enclosing the ribbon cross-section.

6.7.3 Basis line

The basis line is that line in the cross-section of an optical fibre ribbon crossing the fibre centres of the first fibre (fibre 1) and the last fibre (fibre n) of the fibre ribbon, as shown in Figure 1 as dotted line. This line is used as the reference plane for the fibre alignment measurements.

6.7.4 Fibre alignment

6.7.4.1 Horizontal fibre separation

The horizontal separation of fibres is the distance of the orthogonal projection of two fibre centres on the basis line in the fibre ribbon cross-section.

Two horizontal separation parameters can be distinguished:

- a) centre-to-centre distance d between adjacent fibres;
- b) centre-to-centre distance b between the extreme fibres.

6.7.4.2 Planarity

The planarity p of the fibre ribbon structure is the sum of the maximum positive and absolute value of the maximum negative vertical separation of the fibres.

The vertical separation of the fibres is the orthogonal distance from the fibre centre to the basis line. The vertical separation is positive for fibres "above" the basis line and negative for fibres "below" the basis line.

7 Method G3: Ribbon dimensions – Aperture gauge

7.1 Object

The purpose of this test is to verify the functional performance of a ribbon. In order to ensure functional performance, the dimensions of edge bonded ribbons may be controlled and verified for final inspection purposes with an aperture gauge. The intent is to verify that the end portion of a ribbon can be inserted into and would be reasonably aligned to the guide slots of commercial stripping tools.

7.2 Sample

Unless otherwise specified in the detail specification, five representative ribbon samples, each with a minimum length of 50 mm, shall be taken from the ribbon to be tested.

7.3 Apparatus

An aperture gauge, as shown in Figure 2 shall be used to assess the overall dimensions of a ribbon. The values for ribbon width (w) and ribbon height (h) of Figure 2 shall be the nominal ribbon dimensions as established using method G2 in an appropriate quality assessment scheme.

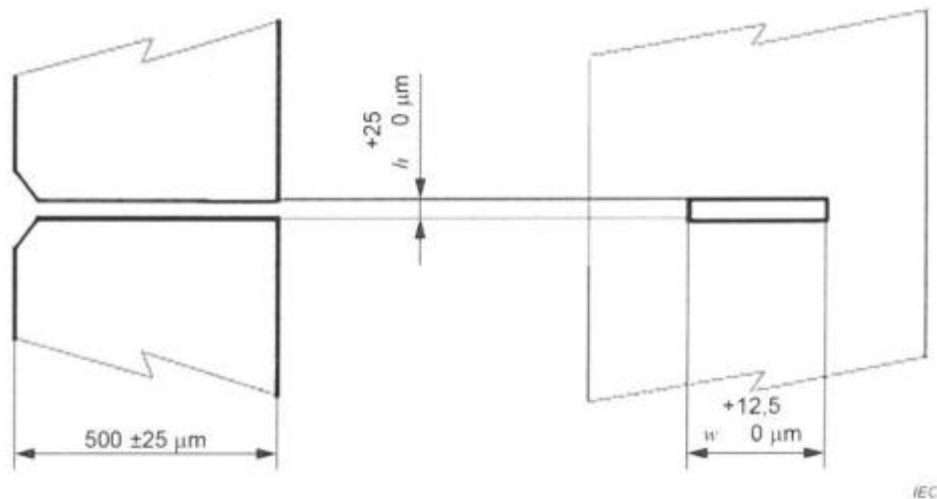


Figure 2 – Aperture gauge

7.4 Procedure

The ribbon sample to be tested is held in the middle, and a 10 mm end portion is inserted through the aperture gauge.

7.5 Requirement

It shall be possible for the 10 mm ribbon end portion to be freely inserted through the aperture gauge without mechanical damage to the sample.

7.6 Details to be specified

The detail specification shall include the following:

- a) dimensions of the aperture gauge;
- b) number of samples to be tested.

8 Method G4: Ribbon dimensions – Dial gauge (obsoleted method)

9 Method G5: Ribbon tear (separability)

9.1 Object

The purpose of this test is to assure sufficient tear resistance for ribbons where the fibres are not required to be separable, or to assure sufficient separability of the fibres for ribbons where the fibres are required to be separated. The intention of this test is to be able to tear by hand without damage.

9.2 Sample

A number of samples of fibre ribbon, as specified in the detail specification, typically 3 to 5, shall be selected from the ribbon or ribbons to be tested. The length of each sample shall be sufficient to provide the number of test specimens as detailed below.

For an n fibre ribbon, $n/2$ specimens are taken from each of the samples above. Each specimen shall be 100 mm minimum length, consistent with Figure 3.

Prepare the $n/2$ specimens involving increasing numbers of fibres to be separated as a ribbon unit. That is, a specimen for fibre 1; a specimen for fibres 1 to 2; a specimen for fibres 1 to 3; etc.

The fibres to be tested are separated with a knife or other suitable method on a suitable length for clamping, per Figure 3.

For the first sample, the preparation of the test sequence shall be to separate one fibre from the other fibres in the ribbon in the first specimen. Then, separate a unit of two fibres from the next specimen. Then, units of three, four, etc. fibres are separated in the other specimens, up to a unit of $n/2$ fibres in the last specimen.

Do the same preparation for all the other samples.

NOTE If n is an odd number, replace $n/2$ with $(n-1)/2$ in the above description.

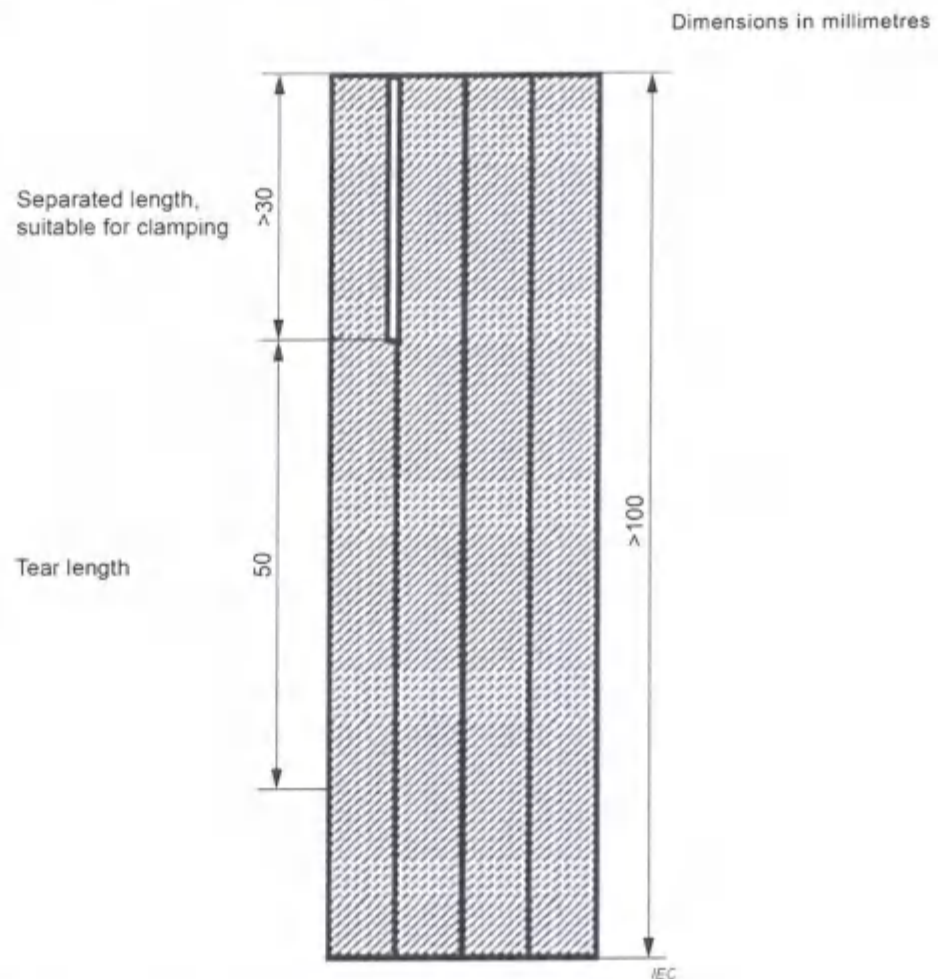


Figure 3 – Sample preparation for ribbon separability test

9.3 Apparatus

The apparatus consists of

- a) a tensile strength measuring apparatus with suitable clamping devices and suitable force recording functions, and
- b) a microscope with at least $100\times$ magnification.

9.4 Procedure

The specimen is inserted into the strength measuring apparatus, as shown in Figure 4. The fibres to be tested are torn at a speed of approximately 100 mm/min to 500 mm/min. The force to tear the fibres on a minimum length of 50 mm is continuously recorded.

In the case where fibres are required to be separated, the primary coating of the separated fibre(s) shall be visually inspected by means of a microscope.

The procedure is repeated for the specimens involving separation of fibre 1, fibres 1 to 2, fibres 1 to 3, etc. up through fibres 1 to $n/2$.

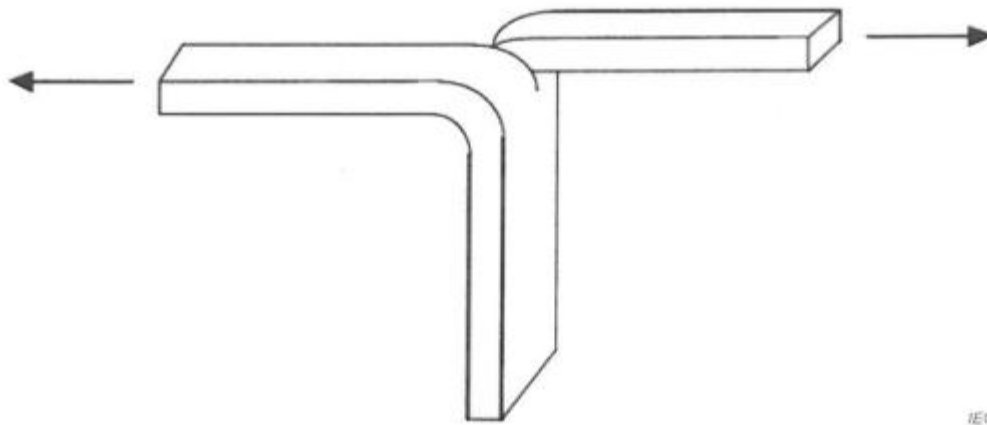


Figure 4 – Separability procedure

9.5 Requirements

The primary requirement is to be able to make the tear without fibre damage (coating damage or fibre breakage). For ribbons where the fibres are required to be separated, the coloured primary coating of the separated fibre(s) shall be effectively free from ribbon matrix residues.

Any colour coding of fibres shall remain sufficiently intact within any 25 mm segment to enable individual fibres to be distinguished from each other.

The minimum or maximum and mean tear forces shall be as specified in the detail specification.

9.6 Details to be specified

The detail specification shall include the following:

- minimum and mean tear force, in N, when fibres are not required to be separated;
- maximum and mean tear force, in N, as required by the detail specification, when fibres are required to be separated;
- number of samples;
- type of ribbon (separable or non-separable).

10 Method G6: Ribbon torsion

10.1 Object

The purpose of this test is to verify the mechanical and functional integrity of the fibre ribbon structure. The test determines the capability of the ribbon to withstand torsion without delamination.


10.2 Sample

Unless otherwise specified in the detail specification, five representative samples, each with a minimum length of 120 mm, are obtained from the ribbon to be tested.

10.3 Apparatus

The testing apparatus, an example of which is in Figure 5, consists of two vertically positioned clamps to hold the sample while it is twisted under a minimum tension of 1 N. The minimum length to be tested is 100 mm.

Dimensions in millimetres

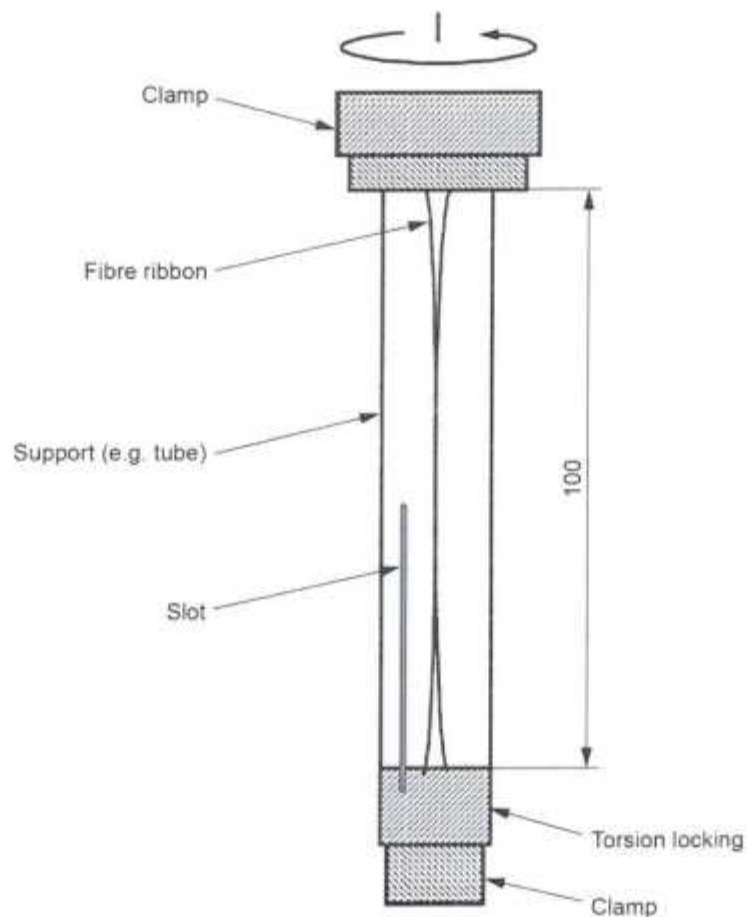

IEC

Figure 5 – Torsion test

10.4 Procedure

The sample is securely fixed in the apparatus and twisted in increments of $180^\circ \pm 5^\circ$ within a time of 2 s. The minimum dwell time after each twist increment is 5 s. The incremental twisting is continued to the value(s) agreed upon between the customer and supplier, as defined in the detail specification, or until delamination occurs.

10.5 Requirements

The ribbon shall withstand the number of 180° turns stated in the detail specification until delamination occurs.

10.6 Details to be specified

The detail specification shall include the following:

- number of samples;
- number of turns.

11 Method G7: Tube kinking

11.1 Object

The purpose of this test is to determine the ability of tubes containing optical fibres to withstand mechanical stresses encountered during cable installation and splicing. The test is carried out on tubes taken from an optical cable.


11.2 Sample

Tube containing fibres, with a length of at least $L_1 + 50$ mm, shall be taken from an optical fibre cable.

Five (5) samples shall be tested, unless otherwise specified.

11.3 Apparatus

The apparatus consists of a testing device as shown in Figure 6.

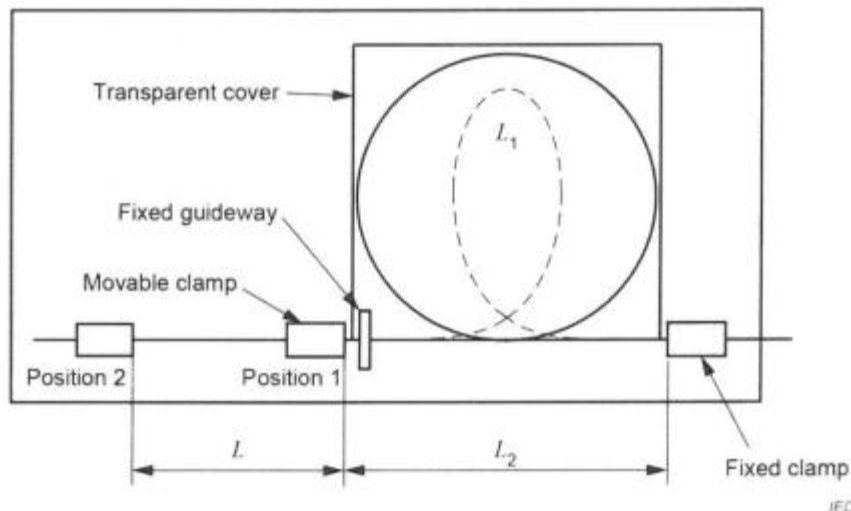

Key

L_1 length of tube under test

L_2 distance between the tube clamping point of the movable clamp and the tube clamping point of the fixed clamp at the start of the test

L moving distance (the length of which determines the reduction of the ellipse dimension)

The minimum diameter of the loop is not fixed by a curvature in the test equipment, but only controlled by the fixed length L_1 of the specimen and the moving length L .

The fixed guideway ensures a defined position of the sample. A transparent cover allows the sample to be kept in the same plane and observed whilst being tested. The distance between the two covers shall be typically three times the tube diameter. Too great a distance will allow the tube to move sideways during the test and does not ensure that the test is severe enough.

Figure 6 – Tube kinking test

Examples of test apparatus dimensions for tube kinking are shown in Table 1.

**Table 1 – Examples of test apparatus dimensions
for tube kinking**

Nominal tube diameter mm	L_1 mm	L_2 mm
$\leq 3,1$	350	100
$\leq 6,1$	650	200
$\leq 10,1$	1 050	300

11.4 Procedure

The test shall be carried out at standard atmospheric conditions.

The sample shall be marked with a length L_1 and mounted in the test device as shown in Figure 6, with the movable and fixed clamps separated by a distance L_2 .

The moveable clamp shall be moved between positions 1 and 2 over a distance L and returned to position 1 at a speed approximately 10 mm/s. This movement is one cycle. During the last cycle, the sample shall remain in position 2 for 60 s.

The values of test parameters L , L_1 , L_2 and the number of cycles (five, unless stated otherwise) should simulate the service deployment conditions. They shall be agreed between customer and supplier.

NOTE 1 Whilst the loop tends to form an ellipse rather than a perfect circle during the test, it is possible to simplify the understanding of the test parameters considerably by assuming that a circle is formed. Based on this assumption, then

$$L = L_1 - (L_2 + \pi \times D) \quad (1)$$

where

D is the tube loop diameter (mm).

NOTE 2 As a mechanical test, a typical minimum value for the tube loop diameter is 60 mm, since this aligns with the minimum specified bend diameter for most classes of fibre and also represents a minimum practical value of coiled tube loops within a joint or other connectivity plant.

NOTE 3 Using $D = 60$ mm, then L can be calculated (for tubes $\leq 3,1$ mm) from Formula (1), which also yields the value of 60 mm. Since the loop does form an ellipse, which makes the effective loop diameter in one plane much more severe, it is possible that 60 mm is taken as the maximum length specified for the moving length, L . Lower values can be specified.

NOTE 4 If this test is used to simulate installation of a tube within a joint, then the value for D can be replaced by the available width within a joint.

11.5 Requirements

During the test, no kinking of the sample shall be visible.

11.6 Details to be specified

The detail specification shall include the following:

- number of cycles (five, unless otherwise specified);
- lengths L , L_1 , L_2 (use $L = 60$ mm, L_1 and L_2 according to Table 1, unless otherwise specified);
- test temperature.

12 Method G8: Ribbon residual twist test

12.1 Object

The ribbon residual twist test, or flatness test, evaluates the degree of permanent twist in a cabled optical fibre ribbon.

12.2 Sample

Ribbon samples shall be taken from a preconditioned (aged) test cable.

The samples shall be of a length sufficient to include the gauge length of 50 cm and additional length on each end to facilitate attachment of clamps and the test weight.

12.3 Apparatus

The apparatus shall be constructed to have the following characteristics.

- The ribbon shall hang vertically, clamped at the top, with the bottom end free to rotate and translate as necessary.
- A mass shall be attached to the bottom end of the ribbon sample, with the gauge length situated between the top clamp and the bottom mass.
- The bottom mass shall be arranged so that it does not impart any twisting or side loading of the ribbon.
- The gauge length shall be 50 cm ± 5 cm, unless otherwise specified.
- The mass shall be 100 g ± 5 g, unless otherwise specified.
- A method shall be provided to measure the axial rotation of the lower end of the ribbon gauge length with respect to the upper end.

12.4 Procedure

Perform the following steps, unless otherwise specified.

- 1) Precondition the ribbon at 85 °C ± 2 °C, uncontrolled relative humidity, for 30 days in its cable.
- 2) Mount one end of the ribbon in the top clamp.
- 3) Attach the bottom mass.
- 4) Allow the ribbon to rotate. When the rotation settles out and the ribbon becomes still, measure the angular rotation of the bottom end of the gauge length with respect to the upper end of the gauge length.
- 5) Calculate the residual twist of the sample according to Formula (2):

$$T = \frac{\theta}{L} \quad (2)$$

where

T is residual twist, °/cm;

θ is final angle from top to bottom, °;

L is measured gauge length, cm.

12.5 Requirements

The calculated residual twist of optical fibre ribbon shall not exceed the maximum residual twist requirements of the detail specification. In most cases, a maximum residual twist of 8°/cm is adequate.

12.6 Details to be specified

The detail specification shall include the following:

- a) the preconditioning conditions, if different from those stated above;
- b) the ribbon gauge length, if different from that stated above;
- c) the tension mass, if different from that stated above.

13 Method G9: Bleeding and evaporation

13.1 Object

The purpose of this test is to measure at high temperature the bleeding and/or evaporation of filling compounds used in contact with optical fibres.

NOTE This method is known as method E15 in IEC 60794-1-21:2015.

13.2 Sample

Filling compound material intended to be used in contact with optical fibres shall be prepared with sufficient amount to perform the test.

13.3 Apparatus

The apparatus consists of

- a) an electric heating cabinet with natural ventilation,
- b) an analytical balance with an error limit $G = 0,1$ mg, and
- c) the test set-up (see Figure 7), consisting of the following:
 - 1) cone, nickel, gauze, 60 mesh (holes: 5,6 per mm²; wire diameter: 0,19 mm; opening: 0,28 mm), with a wire handle;


NOTE 1 Alternatively, the cone can consist of stainless steel (60 mesh, opening 0,25 mm) and the solder width can be more than 1 mm, provided it is proved that the results are not significantly different from the first one.

- 2) a beaker, tall-form, without a spout, 200 ml;

NOTE 2 The cover is not needed when measuring the evaporation.

- 3) a desiccator.

Dimensions in millimetres

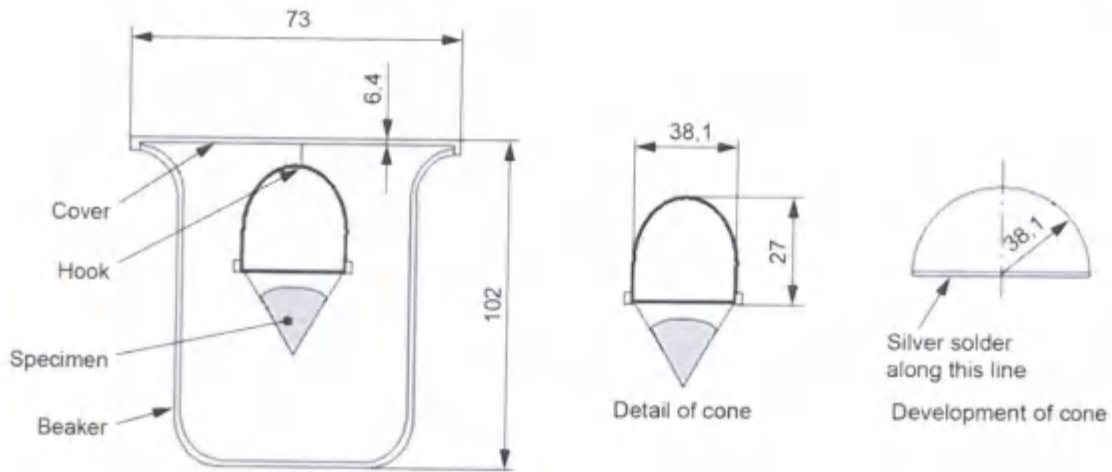

IEC

Figure 7 – Bleeding and evaporation test set-up

13.4 Procedure

Weigh the clean dry beaker and record as M_1 (weighed to within 1 mg). Weigh the assembled beaker, cone and cone support and record as M_2 . Add about 10 g of sample to the cone (the upper surface shall be smooth and convex so that fluid is not trapped and there shall be no aggregate materials in the gauze mesh). Weigh the assembled apparatus and sample and record as M_3 .

Heat the test set-up in the cabinet at the temperature and for the duration stated in the detail specification. Cool to room temperature in the desiccator. Reweigh the assembled apparatus and record as M_4 . Carefully remove the cone support and cone. Reweigh the beaker and record as M_5 . Calculate the percentage bleeding and evaporation according to Formulae (3) and (4) and report the average of the duplicate results.

Calculations:

$$B = \frac{M_5 - M_1}{M_3 - M_2} \times 100 \quad (3)$$

$$E = \frac{M_3 - M_4}{M_3 - M_2} \times 100 \quad (4)$$

where

B is the amount of compound which has bled into the beaker (bleeding), %;

E is the amount of compound missing from the system (evaporation), %.

13.5 Requirements

The reported average results shall not exceed the maximum values given in the detail specification.

13.6 Details to be specified

The detail specification shall include the following:

- a) test temperature;
- b) duration of test;
- c) type of cone to be used if differing from that of 13.3, c), 1);
- d) number of samples to be tested.

14 Method G10A: Stripping force stability of cabled optical fibres

14.1 Object

This test determines the stability of the stripping force of the coating of cabled fibres by measuring the change in fibre strippability after exposure to specified environmental conditions.

NOTE This method is known as method E5A in IEC 60794-1-21:2015.

14.2 Sample

14.2.1 Sample length

The length of the cable or fibre sample shall be sufficient to carry out the specified test.

14.2.2 Sample preparation

The cable from which the fibres shall be taken is preconditioned, as specified in the detail specification, prior to withdrawal of the fibres.

The test shall be carried out on fibres taken from a sample of cable which is further divided into two lengths (minimum 2 m). One length is for testing and the other for reference measurements.

Sufficient samples shall be provided to allow tests to be carried out on 10 test pieces of fibre, conditioned as specified in the detail specification, and compared with test results for fibres taken from the reference cable length.

After withdrawal, any filling compound adhering to the fibres shall be carefully removed (e.g. by wiping with a soft tissue).

14.3 Apparatus

The apparatus consists of conditioning equipment (if necessary) and a fibre strippability apparatus (according to the strippability test method of IEC 60793-1-32:2018).

14.4 Procedure

The optical fibre strippability shall be measured on the environmentally conditioned samples using the strippability method of IEC 60793-1-32:2018, after the recovery time and reconditioning as given in the detail specification. The same method shall be used to measure the strippability of fibre samples taken from the reference cable length, and the change in stripping force shall be determined from a comparison of the results.

Alternatively, samples may be taken from cable aged according to method F9 of IEC 60794-1-22:2017.

14.5 Requirements

The change in stripping force shall meet the requirements specified in the detail specification.

14.6 Details to be specified

The detail specification shall include the following:

- a) cable preconditioning;
- b) fibre conditioning;
- c) recovery time and reconditioning;
- d) permissible change in stripping force.

15 Method G10B: Strippability of optical fibre ribbons

15.1 Object

The purpose of this test is to evaluate the strippability of optical fibre ribbons in terms of fibre cleanliness after coating removal and fibre breakage due to ribbon stripping.

NOTE This method is known as method E5B in IEC 60794-1-21:2015.

15.2 Sample

The test sample shall be representative of the population of ribbons under evaluation.

Samples may be taken sequentially along a length of ribbon, but sections of the ribbon previously in the grips of the stripping tool shall be excluded.

The length of the sample shall be sufficient to allow the matrix and fibre coatings to be removed over a minimum length of 25 mm with a maximum of ten and a minimum of five strips per sample.

Sample environmental conditioning requirements shall be agreed between customer and supplier.

15.3 Apparatus

15.3.1 General

A ribbon stripping apparatus and conditioning equipment (if necessary).

15.3.2 Stripping tool

The results of the test are strongly dependent upon the design of the stripping tool used, and the following tool design guidelines shall be taken into account.

- The mechanical stripping tool shall provide a heated surface that operates at a temperature in the range +70 °C to +140 °C. The heated surface, once set to the specified temperature, shall maintain that temperature within ± 5 °C during the stripping operation. The heated surface(s) shall be located behind the stripping blades and positioned to heat the part of the ribbon in which the coating is to be removed.
 - Heat-up time and dwell time for the tool may be important and the tool manufacturer's recommendations shall be followed.
 - Follow the ribbon manufacturer's recommendations for setting the tool temperature.
- The stripping tool or loading fixture shall maintain a constant pressure sufficient for proper stripping. Care shall be taken that the tool does not begin to open during stripping.
- The size of the gap between the blades shall be known. This dimension and its tolerance shall ensure that the blades cut through the matrix material and fibre coatings without damaging the fibre cladding.

- The condition of the blades can greatly affect the peak strip force and stripping action. The edges of the blades shall be inspected for notches and burrs under normal vision before and after use.
- Replace the blades when they become damaged or blunt or whenever wear is sufficient to affect the results.

15.3.3 Motor and slide (if used)

The motor and slide shall allow repeatable motion with low vibration and fast acceleration. They shall be capable of imparting constant motion, without jerking, to the test ribbon or stripping tool.

If a manual tool is used, the stripping action shall follow these same criteria.

15.4 Positioning and holding equipment

The test sample shall be firmly held in place so that no slippage occurs (a capstan is recommended). The sample ribbon fibres shall be in line (vertically, horizontally and rotationally) with the plane of the stripping motion.

15.5 Alcohol wipe

A non-abrasive cloth or paper material saturated with a suitable alcohol solution shall be used to wipe the fibres after stripping.

15.6 Procedure

Unless otherwise specified, the condition for testing shall be in accordance with controlled ambient conditions. The strip length shall be ≥ 25 mm and the strip velocity shall be as given in the detail specification (between 100 mm/min and 500 mm/min).

Turn on the test apparatus and allow the tool temperature to stabilize.

Ensure that the area around both blades of the stripping tool is free from debris from any previous use and that the blades are clean.

Strip the ribbon following the manufacturer's recommendation on heating dwell time prior to stripping.

After stripping, wipe the stripped fibres with the alcohol wipe and inspect them visually at a magnification of at least 2X.

Assess the cleanliness and integrity of the fibres after stripping as indicated in Table 2.

Table 2 – Condition of stripped samples

Rating	Condition of stripped sample
1	Coating and matrix materials leave no residue after one or two alcohol wipes
2	Coating and matrix material crumbles or breaks up leaving a heavy residue upon stripping, and multiple alcohol wipes are required to remove residue on the fibres. Fibres are capable of being wiped clean without a second strip.
3	Incomplete strip, some fibre coating remains intact. Multiple strips and alcohol wipes are required to remove all visible residue from the fibres.
4	Failed strip: <ul style="list-style-type: none"> – one or more fibres break; – fail to strip within the required speed.

Carry out the number of strips as given in the detail specification and calculate the average cleanliness rating for each sample, rounded to the nearest whole number.

15.7 Requirements

The average cleanliness rating shall comply with the values given in the detail specification.

No fibres shall break.

15.8 Details to be specified

The detail specification shall include the following:

- a) type of stripping apparatus;
- b) average dwell time;
- c) stripping tool temperature;
- d) stripping velocity;
- e) strip length;
- f) sample environmental conditioning;
- g) required average cleanliness rating;
- h) number of fibres in the ribbon.

16 Method G10C: Strippability of buffered optical fibres

16.1 Object

This test determines the stability of the stripping force of buffered optical fibres.

Tests to evaluate two types of buffers are included: tight buffer fibres, where the buffer is in intimate contact with the fibre's outer coating, and loosely-bound buffer fibres, where the buffer is designed to be removable while leaving the fibre coating intact.

NOTE This method is known as method E5C in IEC 60794-1-21:2015.

16.2 Sample

Samples of buffered fibre to be tested shall comply with the requirements of method G10A.

16.3 Apparatus

The apparatus shall comply with the requirements of method G10A.

The fibre stripping apparatus shall have sufficient clearance to accommodate the buffer to be stripped.

In the case of loosely-bound buffer, the cutting surfaces of the fibre stripping apparatus shall be sized such that the coating of the fibre beneath the buffer is not cut or damaged by the stripping operation.

16.4 Procedure

Follow the procedure of method G10A.

If comparison of unaged and aged samples is specified, perform the procedure as follows, following the intent of method G10A.

- Set aside unaged control samples for later test.
- Age the buffered fibre in the cable or in a representative environment in the lab (in filling compound, or the like, as appropriate) as specified in the detail specification. Ageing according to method F9 of IEC 60794-1-22:2017 is generally appropriate.
- After ageing, remove the samples from the cable or other for strip testing.
- Perform the stripping of the control samples and the aged samples per method G10A.

16.5 Requirements

The buffered fibres shall meet the strippability or strippability stability requirements of the detail specification.

16.6 Details to be specified

The detail specification shall include the following:

- a) cable preconditioning, if any;
- b) fibre conditioning;
- c) recovery time and reconditioning;
- d) permissible change in strip force or maximum/minimum strip force.

17 Method G11A: Tensile strength and elongation of buffer tubes and micro tubes at break

17.1 Object

These tests are to determine the tensile strength and elongation at break of the buffer tubes of the cable and micro tubes in the condition as manufactured (i.e. without any ageing treatment) and, when required, after one or more accelerated ageing treatment(s), which are prescribed in the relevant cable standard.

When the ageing treatment is to be carried out on prepared test pieces (in accordance with IEC 60811-401), the test pieces for the ageing treatment shall be from positions adjacent to the test pieces used for the test without ageing and the tensile tests on the aged and unaged test pieces shall be made in immediate succession.

NOTE 1 This method is included in IEC 60811-501.

Where further increased test reliability is necessary, it is recommended that the tests on aged and unaged test pieces are performed by the same person using the same testing method and the same apparatus, in the same laboratory.

NOTE 2 In 17.2 to 17.5, descriptions for buffer tube also include micro tube.

17.2 Sample

17.2.1 General

One sample of each buffer tube to be tested shall be taken of sufficient size to provide a minimum of five test pieces each for the tensile tests without ageing and the tensile tests after each of the required ageing treatments, bearing in mind that a 100 mm length is needed for the preparation of each test piece.

Any sample that shows signs of mechanical damage shall not be used for the test.

17.2.2 Preparation and conditioning of test pieces

- a) Conditioning of test pieces

1) Elevated temperature conditioning

NOTE 1 Elevated temperature conditioning is not an ageing treatment. It is used as a means of ensuring stable and consistent test pieces when required. It is used a) when called for in the relevant cable standard, or b) if there is a doubt or disagreement about a result and the test needs to be repeated. In either case, the conditioning applies only to the test piece as taken from the cable before any subsequent treatment (ageing, compatibility test, oil immersion, etc.).

Where conditioning at elevated temperature is used, such conditioning shall be carried out as follows:

- for dumb-bells:
 - i) after the removal of the buffer tube from the cable but before the cutting of strips;
 - ii) after grinding (or cutting) to obtain parallel surfaces.

Where grinding (or cutting) is not needed, the conditioning shall be performed at the point in the test protocol according to i);

- for tubular test pieces: after removal of the fibre, and any filling compound, but before applying the reference marks, if any, for measurement of the extension.

Where the relevant cable standard calls for conditioning at elevated temperature, it shall be for the time and temperature given in that standard. Where, in case of doubt, the test has to be repeated, the conditioning shall be 24 h at $70\text{ °C} \pm 2\text{ °C}$, or a lower temperature corresponding to the maximum operating temperature of the cable.

2) Room temperature conditioning

Before determination of the cross-sectional area, all test pieces shall be protected from direct sunlight and maintained for at least 3 h at a temperature of $23\text{ °C} \pm 5\text{ °C}$.

b) Dumb-bell test pieces

Dumb-bell test pieces shall be used whenever possible. They shall be prepared from samples of buffer tube, cut open in the direction of the axis.

Each sample of buffer tube shall be cut into strips of an appropriate length. The strips shall be marked to identify the sample from which they are cut and their positions relative to each other in the original sample.

The strips of buffer tube shall be ground or cut, so as to obtain two parallel smooth surfaces between the reference marks mentioned below, care being taken to avoid undue heating. An example of a cutting machine is given in 17.3. For polyethylene (PE) and polypropylene (PP) buffer tube, cutting only, not grinding, shall be employed. After cutting or grinding, including any removal of burrs, the thickness of the strips shall not be less than 0,8 mm and not more than 2,0 mm. If it is not possible to prepare dumb-bell test pieces that comply with the minimum thickness of 0,8 mm, then tubular test pieces shall be used. If tubular test pieces cannot be prepared, then dumb-bells thinner than 0,8 mm may be used, but the rate of separation shall be 25 mm/min.

The test report should also include the fact that non-compliant dumb-bells were used and that the result is indicative.

For certain tests, a minimum thickness may be required, for instance for the ozone resistance test (IEC 60811-403) and the mineral oil immersion test (IEC 60811-404).

A dumb-bell test piece, in accordance with Figure 8, shall then be punched from each prepared strip of buffer tube, or if possible, two dumb-bell test pieces shall be punched side by side.

In order to improve the reliability of the results, the following is recommended:

- the punch should be very sharp to minimize imperfections in the test piece;
- a cardboard or other suitable support should be placed between the strip and the base plate; this support shall be marked during punching, but not completely cut through by the punch;
- burrs on the sides of the test piece should be avoided.

For materials where punching results in burrs, the following method may be used:

- 1) each end of the punch shall have a groove approximately 2,5 mm wide and 2,5 mm high (see Figure 10);

- 2) the cut dumb-bell test pieces shall remain attached at both ends with the strip previously prepared according to the requirements of 17.2.2 b) (see Figure 11);
- 3) with the machine given in 17.3, an additional 0,10 mm to 0,15 mm thickness can be cut away to remove possible burrs resulting from the dumb-bell punch; when this operation is completed, the dumb-bell test pieces shall be cut through at their ends in order to remove them from the strip.

When the diameter of the core is too small to allow the dumb-bell to be cut in accordance with Figure 8, then a smaller dumb bell test piece in accordance with Figure 9 shall be punched from each prepared strip.

The central 20 mm for the larger dumb-bells or 10 mm for the smaller dumb-bells shall be marked on each test piece, immediately before the tensile test.

NOTE 2 Where a contact extensometer is used, the pre set grips at the required spacing are deemed to constitute a mark.

Dumb-bell test pieces with incomplete ends are permitted, provided that the breaking point occurs between the reference marks.

c) Tubular test pieces


Tubular test pieces shall be used only when the dimensions of the buffer tube are such that it is not possible to prepare dumb-bell test pieces.

The samples of buffer tube shall be cut into pieces approximately 100 mm long and the fibre and any filling compound removed, care being taken not to damage the buffer tube. The tubes shall be marked to identify the sample from which they were prepared and their relative positions in the sample.

The central 20 mm shall be marked immediately before the tensile test.

NOTE 3 Where a contact extensometer is used, the pre set grips at the required spacing are deemed to constitute a mark.

Dimension in millimeters

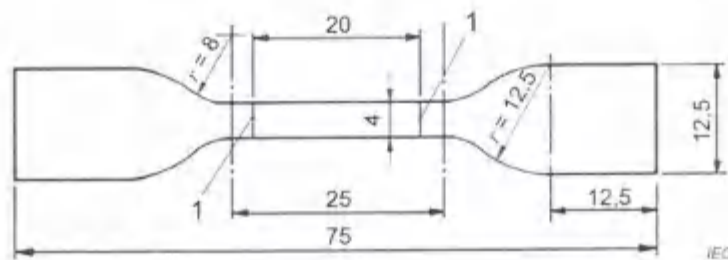


Key

- 1 reference marks

Figure 8 – Dumb-bell test piece

Dimensions in millimeters

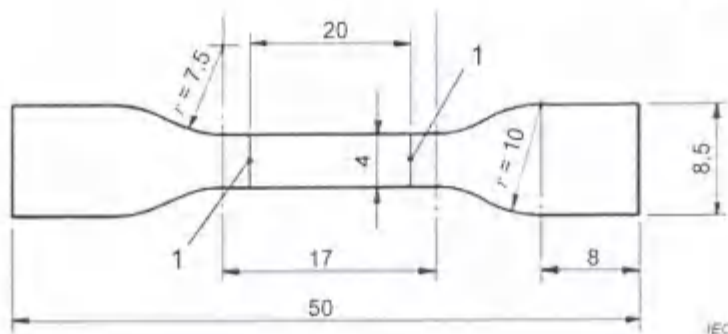


Key

- 1 reference marks

Figure 9 – Small dumb-bell test piece

Dimensions in millimeters

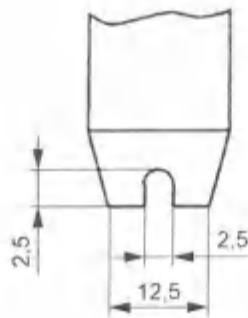

IEC

Figure 10 – Punch end showing groove



IEC

Figure 11 – Test pieces cut by grooved punch

17.2.3 Determination of cross-sectional area

a) Dumb-bell test piece

The cross-sectional area of each test piece is the product of the common width and the measured individual minimum thickness which shall be determined as follows.

For the width:

- the common width is the minimum width of three, randomly selected test pieces;
- if there is doubt about the uniformity of the width, this shall be measured at three positions on the top and the bottom side of the three test pieces. The mean of the top and bottom side measurements shall be calculated for each position. The common width shall be the minimum of the nine mean values determined on the three test pieces;
- in the case of further doubt, the width is measured on each individual test piece.

For the thickness:

- the thickness of each test piece is the minimum of three thickness measurements carried out in the area to be stretched.

The measurements shall be carried out by an optical instrument or by a dial gauge giving a contact pressure not exceeding 0,07 N/mm².

The instrument shall be capable of measuring the thickness with an error of not more than 0,01 mm and the width with an error of not more than 0,04 mm.

In case of doubt, where technically possible, an optical instrument shall be used. Alternatively, a dial gauge with a maximum contact pressure of 0,02 N/mm² may be used.

An appropriate curved foot of the dial gauge should be used if the central part of the dumb-bell is still curved.

b) Tubular test piece

In the middle of the sample being used to prepare the test pieces, a piece shall be taken to determine the cross-sectional area, A , in square millimetres, of the test piece, using one of the following methods. In case of doubt, the methods 2) and 3) shall be used.

- 1) From the dimensions, using the formula:

$$A = \pi (D - \delta) \delta$$

where

δ is the mean value of the thickness of the buffer tube, in millimetres, rounded off to two decimal places;

D is the mean value of the outer diameter of the test piece, in millimetres, rounded off to two decimal places.

- 2) From the density, the mass and the length, using the formula:

$$A = \frac{1000 m}{d \times l}$$

where

m is the mass of the test piece, in grams, to three decimal places;

d is the density, in grams per cubic centimetre, to three decimal places;

l is the length, in millimetres, to one decimal place.

- 3) From the volume and the length, the volume being determined by means of immersion in, for example ethyl alcohol, using the formula:

$$A = \frac{V}{l}$$

where

V is the volume, in cubic millimetres, to two decimal places;

l is the length, in millimetres, to one decimal place.

Care shall be taken to avoid air bubbles in or on the surface of the test piece during immersion.

- c) Sequence of determination of cross-sectional area and ageing

For test pieces which are to be aged, the cross-sectional area shall be determined before ageing treatment.

17.2.4 Ageing treatment

Each required ageing treatment shall be carried out on a minimum of five test pieces (see 17.2.1) in accordance with IEC 60811-401, under the conditions specified in the relevant cable standard.

17.3 Apparatus

A calibrated tensile test machine shall be used.

For the tubular test pieces, in order to avoid damage on samples because of clamping and to get stable results, using the following in the clamping section is recommended:

- rigid inserts whose diameters are similar to the inner diameter of the buffer tube;
- close-to-tube diameter shape clamps.

NOTE 1 As buffer tubes have a kind of rigid behavior, their structures are susceptible to be fractured at the clamping section when using plain clamps with the result of breakage in the clamping section which will get inconsistent values from mechanical evaluations.


An example of a cutting machine is given in Figure 12.

Two rolls, one made of steel and partly grooved (1), and the other, in rubber-tyred steel (2), drive the strip (3) against a highly sharpened fixed, or moving blade (4) (surgical scalpel quality).

The strip is longitudinally cut into two parts: part (5) from which the test piece is cut, and part (6), which is rejected.

The thickness of part (6) can be limited to 0,1 mm if necessary. For this purpose, consideration should be given to the behaviour of the material prepared and the preservation of the blade sharpness.

When the strip (3) has marks of tearing or scratching, which may induce a premature break, it is recommended that part (6) be cut and rejected from both sides.

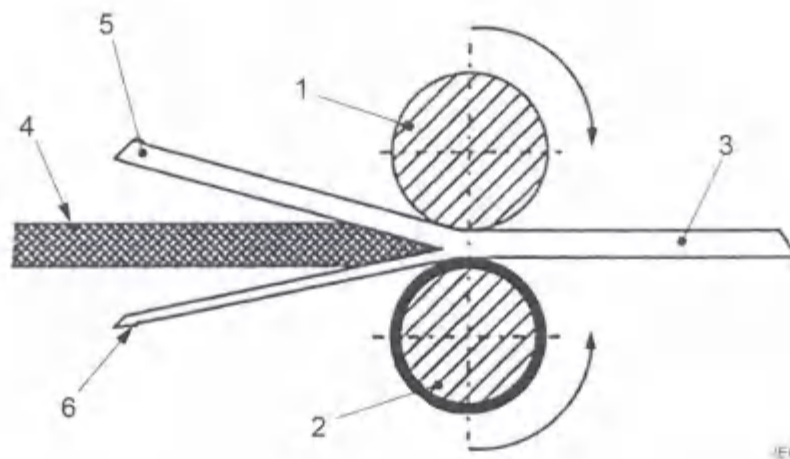

Key

- | | | | |
|---|----------------------------|---|-----------------------------------|
| 1 | steel roll, partly grooved | 4 | blade, fixed or moving |
| 2 | steel roll, rubber-tyred | 5 | part of strip used for test piece |
| 3 | strip | 6 | rejected part of strip |

Figure 12 – Machine for preparing test pieces

17.4 Procedure

The test procedure shall be as follows:

a) Test temperature

The test shall be carried out at a temperature of $23\text{ °C} \pm 5\text{ °C}$.

b) Distance between the grips and rate of separation

The grips of the tensile testing machine may be either of a self-tightening type or not. The total length between the grips shall be about:

- 34 mm for dumb-bells as illustrated in Figure 9;
- 50 mm for dumb-bells as illustrated in Figure 8;
- 50 mm for tubes, if tested with self-tightening grips;
- 85 mm for tubes, if tested with non-self-tightening grips.

The rate of separation, except for PE and PP buffer tubes, shall be $250\text{ mm/min} \pm 50\text{ mm/min}$ and, in case of doubt, $25\text{ mm/min} \pm 5\text{ mm/min}$.

For PE and PP, or buffer tubes containing these materials, the rate of separation shall be $25\text{ mm/min} \pm 5\text{ mm/min}$, but for routine tests, separation rates up to $250\text{ mm/min} \pm 50\text{ mm/min}$ are permitted.

c) Measurements

The maximum tensile force during the test shall be measured and recorded and the distance between the two reference marks at breaking point shall be measured on the same test piece.

An unsatisfactory result due to any test piece breaking due to damage in the grips shall be ignored. In this event, at least four valid results shall be obtained in order to calculate the tensile strength and elongation at break; otherwise, the test shall be repeated.

17.5 Requirements

The buffer tubes shall meet the tensile strength and elongation requirements of the detail specification. Details to be specified.

The detail specification shall include the following:

- a) buffer tube preconditioning, if any;
- b) dimensions of the dumb-bell test piece or tubular test piece;
- c) number of samples to be tested.

18 Method G11B: Elongation of buffer tubes and micro tubes at low temperature

18.1 Object

These tests are to determine the elongation of the buffer tubes and micro tubes at low temperature.

NOTE 1 This method is included in IEC 60811-505.

NOTE 2 In 18.2 to 18.6, descriptions for buffer tube also include micro tube.

18.2 Sample

18.2.1 General

Each buffer tube to be tested shall be represented by two samples of suitable length.

18.2.2 Preparation of test pieces

After all covering has been removed, the buffer tube shall be cut open in the direction of the axis, after which the fibre and any filling compound, if any, shall be removed.

The test is intended for buffer tubes circular cross-section having an external diameter greater than 12,5 mm and for sector-shaped cores large enough to prepare dumb-bells described in 17.2.2. Where it is not possible to prepare dumb-bells, the tubular test pieces described in 17.2.2 are suitable for testing the performance of cores of smaller diameter.

The buffer tube need not be ground or cut if the inner and outer surfaces are smooth, and its mean specified thickness does not exceed 2,0 mm. Samples having a thickness exceeding this limit, or samples having imprints or ridges on the inner side, shall be ground or cut to obtain two parallel and smooth surfaces, and a thickness which does not exceed 2,0 mm. The minimum thickness after grinding or cutting shall be 0,8 mm but if the original thickness of the buffer tube does not allow it, then 0,6 mm shall be permitted as the minimum thickness. Grinding and cutting shall be carefully carried out to avoid undue heating and mechanical stresses in the buffer tube.

All strips shall be conditioned at $23\text{ °C} \pm 5\text{ °C}$ for at least 3 h.

After this preparation, two dumb-bells from each sample in accordance with Figure 8, or if necessary Figure 9, shall be punched in the direction of the axis of each sample; if possible, two dumb-bells shall be punched side by side.

If an apparatus is used which allows the direct measurement of the distance between the marker lines during the test, the dumb-bells shall be marked in accordance with 17.2.2.

18.3 Apparatus

The test may be carried out on a machine provided with a cooling device or on a machine installed in a cooling chamber.

Using a liquid as the refrigerant, the conditioning time shall be not less than 10 min at the specified test temperature.

When cooling in air, the conditioning time for cooling the apparatus and test piece together shall be at least 4 h. If the apparatus has been pre-cooled, this period may be reduced to 2 h, and if the apparatus and test piece have been pre-cooled, the conditioning time after the test piece has been fixed in the apparatus shall be not less than 1 h.

If a liquid mixture is used for cooling, it shall not impair the buffer tube.

18.4 Procedure

The grips of the tensile apparatus shall be of a non-self-tightening type. In both pre-cooled grips, the dumb-bell shall be clamped over the same length.

The free length between the grips shall be about 30 mm for both types of dumb-bells if the direct measurement of the distance between the marker lines is to be made during the test.

If the displacement of the grips is to be measured, the free length between the grips shall be $30 \text{ mm} \pm 0,5 \text{ mm}$ for the dumb-bell in accordance with Figure 8, and $22 \text{ mm} \pm 0,5 \text{ mm}$ for the dumb-bell in accordance with Figure 9.

The speed of separation of the grips of the tensile machine shall be $25 \text{ mm/min} \pm 5 \text{ mm/min}$.

The test temperature shall be as specified in the relevant cable standard.

The elongation shall be determined by measuring the distance between the marker lines, if possible, or between the grips at the moment of the rupture.

For calculating the elongation, the increase of the distance between the marker lines shall be related to the initial distance of 20 mm (or 10 mm if the dumb-bell in accordance with Figure 9 is used), and expressed as a percentage of this distance.

If the alternative method of measuring the distance between the grips is used, the increase of this distance shall be related to the original distance, being 30 mm for the dumb-bell in accordance with Figure 8, and 22 mm for the dumb-bell in accordance with Figure 9. When this method is used, the test piece shall be examined before being removed from the apparatus; if the test piece has partly slipped out of the grips, the result shall be ignored. At least three valid results are required for calculating the elongation, otherwise the test shall be repeated.

Unless otherwise specified, none of the valid results shall be less than 50 %. In case of dispute, the method employing marker lines shall be used.

18.5 Requirements

The buffer tube shall meet the elongation requirements of the detail specification.

18.6 Details to be specified

The detail specification shall include the following:

- a) buffer tube preconditioning, if any;
- b) test temperature;
- c) dimensions of the dumb-bell test piece or tubular test piece;
- d) number of samples to be tested.

Bibliography

IEC 60793-1-50:2014, *Optical fibres – Part 1-50: Measurement methods and test procedures – Damp heat (steady state) tests*

IEC 60793-1-51:2014, *Optical fibres – Part 1-51: Measurement methods and test procedures – Dry heat (steady state) tests*

IEC 60793-1-52:2014, *Optical fibres – Part 1-52: Measurement methods and test procedures – Change of temperature tests*

IEC 60793-1-53:2014, *Optical fibres – Part 1-53: Measurement methods and test procedures – Water immersion tests*

IEC 60794-1-21:2015, *Optical fibre cables – Part 1-21: Generic specification – Basic optical cable test procedures – Mechanical tests methods*

IEC 60794-1-22:2017, *Optical fibre cables – Part 1-22: Generic specification – Basic optical cable test procedures – Environmental tests methods*

IEC 60811-403, *Electric and optical fibre cables – Test methods for non-metallic materials – Part 403: Miscellaneous tests – Ozone resistance test on cross-linked compounds*

IEC 60811-404, *Electric and optical fibre cables – Test methods for non-metallic materials – Part 404: Miscellaneous tests - Mineral oil immersion tests for sheaths*

IEC 60811-501, *Electric and optical fibre cables – Test methods for non-metallic materials – Part 501: Mechanical tests – Tests for determining the mechanical properties of insulating and sheathing compounds*

IEC 60811-505, *Electric and optical fibre cables – Test methods for non-metallic materials – Part 505: Mechanical tests – Elongation at low temperature for insulations and sheaths*

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

3, rue de Varembe
PO Box 131
CH-1211 Geneva 20
Switzerland

Tel: + 41 22 919 02 11
Fax: + 41 22 919 03 00
info@iec.ch
www.iec.ch